

INVESTIGATION OF THE USE OF POLYSTYRENE PLASTIC WASTE AS COARSE AGGREGATES IN CONCRETE

Marc Adrian Kung¹, Albino Sablayan IV¹, *Daniel Nichol Valerio¹, Ma Klarissa Daly¹ and Kenneth Jae Elevado¹

¹Department of Civil Engineering, De La Salle University, Philippines

*Corresponding Author, Received: 15 July 2023, Revised: 05 Oct. 2024, Accepted: 10 Oct. 2024

ABSTRACT: Concrete is the most widely used construction material, but its production consumes a large amount of natural resources and generates significant carbon emissions. In recent years, there has been growing interest in using waste materials and recycled products in concrete production to reduce its environmental impact. This study investigates the use of polystyrene plastic as a replacement for gravel in concrete production, particularly for structural applications. A mixed design methodology was employed to prepare three different concrete mixtures: conventional concrete, polystyrene concrete, and coated polystyrene concrete. The main findings of this study indicate that the full replacement of gravel with polystyrene plastic achieved the minimum compressive strength required for structural use. The study also demonstrated that using polystyrene plastic in concrete can reduce its overall weight and improve workability. The significance of this research lies in its potential to reduce the environmental impact of concrete production by incorporating recycled plastic waste as a substitute for natural resources. This study provides valuable insights into the use of polystyrene plastic in concrete, which could inform the development of more sustainable construction practices in the future.

Keywords: Polystyrene, Replacement, Plastic waste, Concrete, Waste utilization

1. INTRODUCTION

In the 21st century, there has been a substantial increase in plastic garbage, which has become a problem. Scientists estimated that humans produced over 8300 million metric tons (Mt) of virgin plastics in 2017, with about 6300 Mt of plastic trash produced as of 2015. Only about 9% of this garbage had been recycled. Most plastic products typically end up in landfills or the ocean after being used. Plastic items may take 100 to 1000 years to degrade, and there is a decreasing number of landfills that can accommodate waste. With that, this global problem should be stopped from getting worse [1].

In recent years, there has been growing interest in using waste materials and recycled products in concrete production to reduce its environmental impact [2-6]. Polystyrene (PS) is one of the several waste materials that can be an alternative to the conventional concrete aggregates. PS is a synthetic polymer made from monomers of the aromatic hydrocarbon styrene [7]. PS contains an expansion gas known as pentane dissolved within the polystyrene bead. When the polystyrene bead is exposed to heat, the small amount of gas would expand which would form closed cells of Expanded Polystyrene (EPS).

Since plastic is a non-biodegradable product which stays for many decades in the ecosystem. Therefore, different solutions in the field of civil engineering have been done to help mitigate this plastic problem. Plastic has been applied in different engineering structures by making it a substitute for

construction materials [2-4]. With this, the quantity of different materials used in construction can be reduced. Other than that, more solutions to solving the plastic waste problems evolved where plastics can be an alternative in the construction industry.

This paper is heavily influenced by the studies of Nursyamsi and Purnomo, Pamundji, & Satim [8, 9]. Both studies have investigated the compressive strength of concrete that uses plastic waste as an alternative coarse aggregate. It is important to note that according to the ACI 318 Standard, Section 5.1.1, the minimum specified compressive strength of structural concrete is 2500 psi or 17.23 MPa.

The study of Nursyamsi used PET plastic waste as an alternative to the coarse aggregate of concrete [8]. The methodology used in creating the plastic coarse aggregate in this study replicates the size and shape of natural coarse aggregate used in creating concrete. The fineness modulus of the coarse aggregate that achieved the maximum compressive strength is FM 7 with 16.57 MPa.

On the other hand, the study of Purnomo et al. in 2017 used polypropylene (PP) plastic waste as coarse aggregate [9]. The coarse aggregate was molded into a plastic cube of 10 mm of thickness, 20 mm of length, and 20 mm of width. The study underwent two types of plastic specimens, where the coated plastic specimen was mixed with sand and uncoated plastic specimen remained as is. The results showed that the coated plastic specimen had a better bonding than the uncoated plastic specimen, as it revealed fewer cracks between the aggregate and mortar. The fineness modulus of the coarse aggregate was 4.45. The

uncoated plastic achieved 14.25 MPa, while the coated plastic aggregate achieved 17.5 MPa, which was the minimum required compressive strength for structural concrete.

Plastic aggregates used as fine or coarse aggregates have a disadvantage in their mechanical properties when compared to natural aggregates. These are caused by a low bond strength between the surface of the plastic aggregate and the cement paste, and as plastic is a hydrophobic material, it limits the water movement within the mixture [10]. However, improving the characteristics of the surface of plastic aggregates by amplifying the hardness and texture would enhance the mechanical properties of plastic aggregate with mortar [11].

Furthermore, the use of sand coating on the Polystyrene coarse aggregates would provide more surface area for water and cement to bind with. As plastics are known to be hydrophobic, while ordinary sand is known to be hydrophilic. Sand coating would provide better workability with the concrete mix and create durable concrete.

2. RESEARCH SIGNIFICANCE

The significance of the study is to promote construction industries to use an alternative material for gravel, such as plastic which would help reduce the ongoing plastic problem in the Philippines. This can help reduce pollution, lessen flooding in communities, and improve the quality of the environment, making a better future for the world. Other than that, it can also aid other civil engineering-related research that aims to help the environment by reducing the global plastic problem. With this, the study lies in its potential to tackle two pressing global challenges: plastic waste management and resource depletion in the construction industry. By replacing gravel with plastic waste, substantial amounts of plastic waste can be diverted from landfills and oceans, thereby reducing its adverse effects on ecosystems and human health. With this replacement, it would reduce the need for gravel extraction, a process that often leads to habitat destruction, soil erosion, and water pollution. By having an alternative approach, the study aims to encourage sustainable consumption and procurement practices within the construction industry, contributing directly to SDG 12: Responsible Consumption and Production.

3. METHODOLOGY

The methodology employed in this study involved the procurement and utilization of two distinct types of Polystyrene coarse aggregate, namely uncoated Polystyrene, and sand-coated Polystyrene. The plastic aggregates were sourced from a reliable supplier specializing in Polystyrene plastic materials. The procurement process ensured the acquisition of clean, high-quality plastic aggregate conforming to

the required specifications.

3.1 Materials

The materials used for the study consisted of Ordinary Portland Cement Type 1P, expanded polystyrene coarse aggregates (EPCA), ordinary coarse sand, and water, which are the main materials to create the concrete mix. The concrete samples underwent slump test and compressive strength test, as these are the common tests used to determine if the concrete mix design would achieve the desired slump and if the samples would pass the minimum required compressive strength for concrete.

For the slump test, the materials needed were the slump cone, base, tamping rod, scoop, funnel, measuring tape, and cleaning brush. On the other hand, for the compressive strength test, a cylindrical mold and universal testing machine are needed.

3.2 Plastic Coarse Aggregates

In order to obtain the required EPCA, the researchers contacted Pakvite Manufacturing Corporation to aid in manufacturing. Pakvite Manufacturing Corporation manufactures food container products that are made from Styrofoam. Styrofoam is made up of Polystyrene, Calcium stearate, and Talc. Calcium stearate and Talc are used as a thickening agent and lubricant, as Styrofoam containers are seen to be glossy and smooth. The materials were placed in an extruder, where a polymer material combined with additives was melted and formed into a roll. As the products were produced, there were Styrofoam scraps, which were considered to be the company's waste and were subjected to recycling. The Styrofoam scrap was shredded and placed into an extruder, which produced a long, thin, solid, and cylindrical shape. Afterward, the plastic was submerged in water to cool down. Then, the plastic rods were solidified into a mass with a thickness of 20 mm, as seen in Fig. 1.



Fig.1 Hardened Molded Polystyrene.

The mass was then crushed to the desired size that would pass the 20 mm sieve, as shown in Fig. 2.

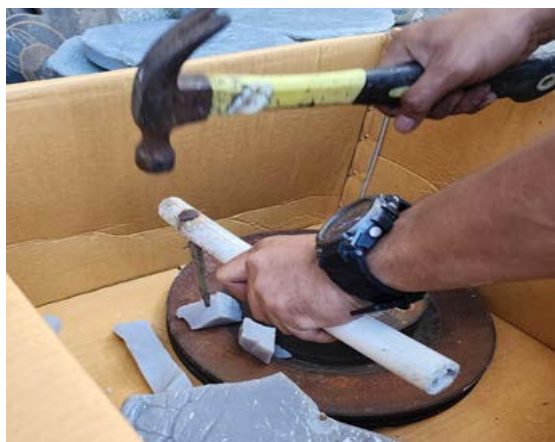


Fig.2 Crushing Polystyrene.

3.3 Coated Polystyrene Coarse Aggregate

In order to produce the coated Polystyrene aggregates, the process began by gathering a sufficient amount of coarse sand, which served as the base material for the coating. The coarse sand was obtained from a local hardware construction store.

To prepare the hot sand, a heat source, such as a burner or a furnace, was utilized. The sand was placed in a container that was exposed to the heat source, allowing it to gradually increase in temperature. The heating process also involved stirring or turning the sand intermittently to ensure an even distribution of heat. While the sand does not require precise temperature control, it should reach a sufficiently high temperature to facilitate the coating process.

Next, the Polystyrene Coarse Aggregates were prepared separately. Once the hot sand and Polystyrene coarse aggregates were prepared, the mixing process took place. The Polystyrene coarse aggregates were transferred to the burner and carefully mixed until the plastic particles were uniformly distributed and coated with the hot sand. This ensured a homogenous blend of the material, resulting in a composite mixture with improved properties.

During the mixing process, the heat from the sand softened the plastic aggregate, enabling it to adhere to the sand particles. The result was a coated mixture where the plastic aggregate became firmly attached to the sand, creating a cohesive composite material.

3.4 Natural Coarse Aggregate and Coarse Sand

The gravel and coarse sand were obtained from KBon Construction Supply located in Quezon City, Philippines. The physical properties of gravel and coarse sand, such as specific gravity, absorption, and moisture content, were obtained using ASTM C127 (Specific Gravity and Absorption), while dry rodded

density was obtained using ASTM C29 (Dry rodded density), and fineness modulus was obtained using ASTM C33 (Fineness modulus of Aggregates).

3.5 Mix Design and Tests

For the concrete mix design, the ACI mix design was followed for the computation. Three mix designs were prepared, as shown in Table 1, where different coarse aggregates were used, namely the sand-coated PS plastic coarse aggregate, PS plastic coarse aggregate, and the conventional coarse aggregate. The researchers were able to produce three mix designs for each coarse aggregate used for the study. Since the two mixed designs have a similar coarse aggregate content, the mixed design that contains the coated polystyrene aggregate requires more water, as there is more sand in total compared to the uncoated polystyrene aggregate.

Table. 1 Mixed Design per 1m3 of concrete.

Type	w/c	Ce (kg)	F (kg)	C (kg)	W (kg)
Sand-Coated PS Plastic	0.76	297.1	843.23	346.1	226
PS Plastic	0.75	297.1	843.23	346.1	223
Conventional Concrete	0.81	302.1	811.45	1004	245

At least five specimens were prepared for sand-coated PS plastic coarse aggregate, PS plastic coarse aggregate, and conventional coarse aggregate. A slump test was carried out using the ASTM C143 after the mixing process. Then, a compressive test was performed after the 28-day curing period in accordance with ASTM C39.

4. RESULTS AND DISCUSSION

Compressive tests were performed on the 28-day-aged concrete cylindrical specimens with a diameter of 10 cm and a height of 20 cm. The results of the compressive strength tests are shown in Tables 2, 3, and 4.

Table 2. Compressive Strength of Concrete Specimen with Conventional Gravel.

CC	Load (kN)	Strength (MPa)	Weight (g)	Time (s)
1	168.18	20.99	3844.5	18.6
2	134.42	16.78	3806.9	17.3
3	159.39	19.89	3897.5	17.7
4	157.47	19.66	3803.8	10.5
5	162.77	20.32	3933.0	14.0
Average	156.45	19.53	3857.14	15.62

Note: CC – concrete specimen.

Table 3. Compressive Strength of Concrete Specimen with Polystyrene Aggregate (PA).

CC	Load (kN)	Strength (MPa)	Weight (g)	Time (s)
1	98.37	12.28	2729.2	13.5
2	103.19	12.88	2757.3	10.9
3	107.67	13.44	2851.2	13.7
4	80.33	10.03	2686.1	11.4
5	82.91	10.35	2723.3	14.2
6	106.31	13.27	2825.5	13.4
Average	96.46	12.04	2762.1	12.85

Note: CC – concrete specimen.

Table 4. Compressive Strength of Concrete Specimen with Coated Polystyrene Aggregate (PSA).

CC	Load (kN)	Strength (MPa)	Weight (g)	Time (s)
1	153.62	19.17	2949.9	13.4
2	167.55	20.91	2966.2	18.4
3	131.70	16.44	2866.0	12.7
4	136.32	17.01	2958.0	13.4
5	156.50	19.53	2910.3	12.6
6	154.29	19.26	2953.3	15.5
Average	150.00	18.72	2933.95	14.33

Note: CC – concrete specimen.

4.1 Slump Test

The results of the slump test showed slumps of around 90 mm to 100 mm for the conventional, plastic, and sand-coated plastic aggregate. The results suggest that the concrete mixture can be used for structural purposes. At first, there were problems encountered in the mix design because the results did not reach the desired slump. This was then adjusted by reducing or increasing the mixing water content by 2 kg/m³ of concrete for each increase or decrease of 10 mm to get the desired slump.

4.2 Physical Appearance of Concrete Specimens

In a study on the compression strength of concrete cylinders, it was found that a significant increase in compressive strength was observed when the fiber content was increased. The increase can be caused by the porosity reduction [12]. Other than that, it can be seen that the cylinders are of the right shape, meaning that there is no leakage present while they cure in the mold. Leakage can disrupt the compression strength of the specimens since a constant area is needed.

4.3 Compressive Strength of Specimens

After subjecting the specimens to a compressive

strength test, it was observed that the concrete specimens that contained uncoated polystyrene coarse aggregate showed weak bonding between the uncoated polystyrene aggregate and mortar. This result is caused by the low hydraulic conductivity of polystyrene, meaning that it does not allow fluid to move easily since the polystyrene used has no pore spaces and does not fracture easily. Another reason would be the hydrophobic characteristics and smooth surface of the uncoated plastic aggregate. Examples of this are shown in Fig. 3.



Fig.3 Rupture of concrete specimen containing uncoated polystyrene aggregates.

The highest compressive strength achieved was 12.88 MPa, which is below the building's minimum structural compressive strength of 17.23 MPa, as stated in the ACI 318 Standard. With these results, it confirms a low compressive strength of concrete containing uncoated plastic coarse aggregates.

To enhance the mechanical properties of the plastic aggregate with the mortar, the methodology of Choi, Moon, Chung, & Cho was used to coat the plastic polystyrene coarse aggregate with sand [11]. It showed a significant increase in the absorption from 0% to 1.47%. With this, the concrete specimens containing coated polystyrene coarse aggregate showed similar results to concrete specimens containing conventional gravel, achieving average compressive strength of 18.72 MPa and 19.53 MPa, respectively. The coated polystyrene coarse aggregate shows high bonding with the mortar, as illustrated in Fig. 4. It was also observed that the increase of compressive strength and less crack appearance proved a high bonding. The highest compressive strength achieved was 20.91 MPa, which reached the building minimum structural compressive strength of 17.23 MPa. Therefore, the results show that concrete containing coated polystyrene coarse aggregates can be used for structural purposes.



Fig.4 Rupture of concrete specimen containing coated polystyrene aggregates.

According to the ACI Committee 213 Guide for Structural Lightweight Aggregate Concrete, lightweight concrete can be classified according to its density, which normally ranges from 320 to 1920 kg/m³ [13]. The calculated density of the concrete specimen containing coated polystyrene coarse aggregates was 1780.36 kg/m³, which is within the numerical range of what is considered to be lightweight concrete. Furthermore, it can be seen in Fig. 5 that the load that the PSA can withstand is close to the results of conventional concrete. The load that conventional concrete can withstand ranges from 134.42 kN to 168.14 kN, while the load that PSA can withstand ranges from 131.70 kN to 163.55 kN. This signifies that the PSA concrete can also be used for structural purposes. However, the same does not apply to the PA specimens since its load capacity only ranges from 80.33 kN to 107.67 kN.

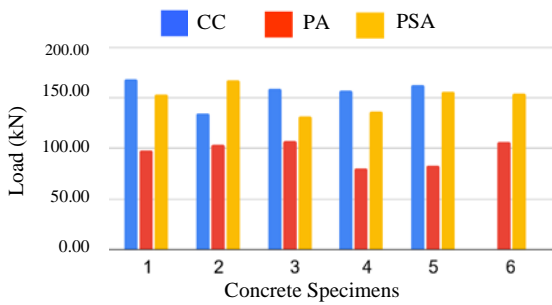


Fig.5 Load per Concrete Specimen.

The average compressive strength and the water-cement (W/C) ratio are shown in Fig. 6. It can be seen that as the compressive strength increased with higher W/C ratio. a higher percentage of water in the mix design was used in the PSA specimens since the aggregates used were covered in sand, which explains the higher W/C ratio obtained.

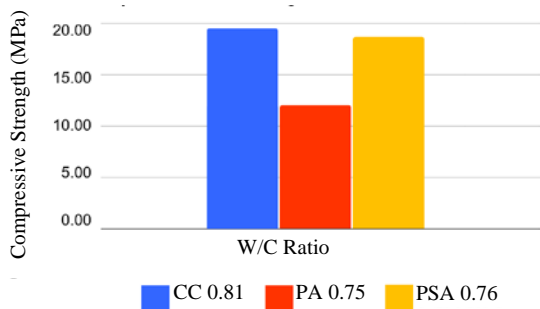


Fig.6 Compressive Strength vs W/C Ratio.

4.4 Stress-Strain Curve and Load Displacement of Concrete Specimens

The purpose of a stress-strain curve is to provide a graphical representation of the relationship between the stress and strain of a material. The values are usually obtained from a tensile stress test, but as per

the limitations of this study, the values were obtained using the compressive stress test.

The load and displacement values were obtained from a displacement transducer, which is an electromechanical device used to convert vibrations into electrical current and to compile the data into a Microsoft Excel file. The strain value was obtained by dividing displacement over the original length of the specimen, while stress was obtained by dividing load over the cross-sectional area of the specimen. Due to budget limitations, only three samples were considered in obtaining the stress-strain curve of each group. The stress-strain curve of PA specimens is shown in Fig. 7. It can be seen that the strain for the PA specimen reaches higher values compared to the strain of the PSA specimen. This is due to the higher compressive strength of the PSA specimen. An increase in the compressive strength of the specimen gives a lower displacement value, thus giving a lower strain value.

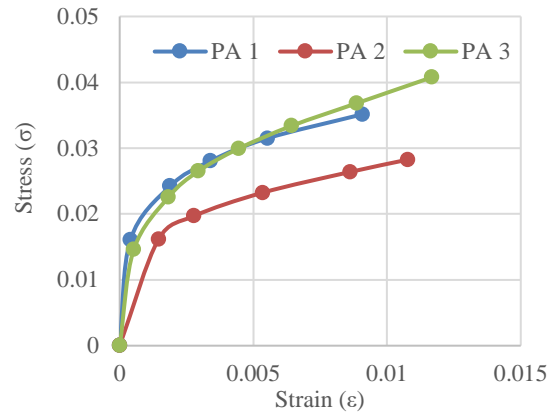


Fig.7 Stress-Strain Curve of PA.

In the PSA stress-strain curve is shown in Fig. 8. It also resembles a typical stress-strain curve. However, in this curve, the line reaching the yield strength of the concrete is much steeper than of the PA stress-strain curve. This shows that the PSA concrete is less brittle compared to the PA concrete.

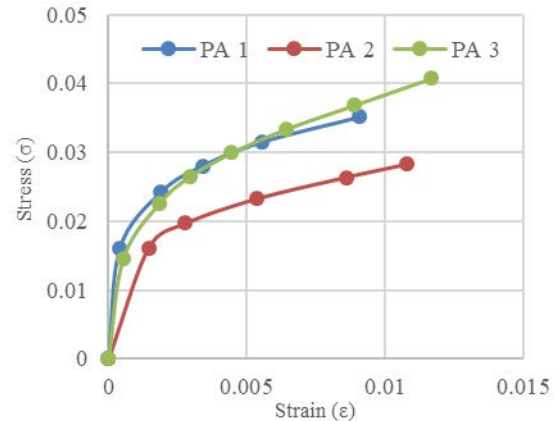


Fig.8 Stress-Strain Curve of PSA.

According to a study by Zhang and Gjvovr, the modulus of elasticity is dependent on the compressive strength of concrete, properties of coarse aggregates, the proportion of the aggregates in the concrete, the quality of cement paste, and additional mineral admixtures [14]. Specifically focusing on the W/C ratio, this crucial factor plays a significant role in determining the properties of concrete, including its modulus of elasticity.

As the W/C ratio increases, the strength to resist deformation decreases proportionally. It can be observed in Table 5 that this study follows the findings of Shelorkar [15]. However, for the PA specimens, it was unable to follow due to low bonding strength and low compressive strength. The modulus of elasticity was obtained from the respective graphs of the stress-strain curve.

It can also be seen that the PA has the lowest modulus of elasticity compared to the other specimens. With this, it can be said that PA is the most brittle among the other specimens. While PSA shows the highest modulus of elasticity which shows that it is the least brittle. This can also be seen in Fig. 7 and Fig. 8 where the elastic region of PSA is steeper compared to PA.

4.5 Concrete Strength Applications

The average compressive strength of conventional concrete, PA, and PSA were determined to be 19.53 MPa, 12.04 MPa, and 18.72 MPa, respectively. Given the compressive strength of conventional concrete and PSA, the types of concrete construction that can be used are basement and foundation walls and slabs, walks, patios, and steps and stairs. As for the PA compressive strength, even if the results did not reach the desired strength value, it can still be used in concrete fills [16]. It is also worth noting that there are aggregate treatment methods that can possibly be employed as part of the methodology to improve the compressive strength results [17].

5. CONCLUSIONS AND RECOMMENDATIONS

The compression testing results of the concrete specimens showed that the concrete containing coated plastic coarse aggregate achieved the minimum compressive strength required for structural use. The addition of a sand coating on the polystyrene surface also improved the bond between the coarse aggregate and the mortar.

Based on the experimental results of this study, it can be concluded that fully replacing gravel with sand-coated polystyrene coarse aggregate in concrete can be viable for structural purposes, while also being classified as lightweight concrete.

Based on the findings and conclusions of this research study, several key recommendations can be made to address the research problem and increase

the accuracy of future results. These recommendations are aimed at bridging identified gaps and improving current practices in using recycled polystyrene as a replacement for gravel. In particular, the following are recommended.

It is advised to explore alternative methods for crushing hardened molded polystyrene. The current method has demonstrated certain limitations in terms of safety and efficiency. Suitable aggregate treatment methods should also be considered to enhance aggregate properties prior to concrete mixing.

The researchers recommend testing compressive strength on the 7th, 14th, and 21st days to more accurately track the strength development of the concrete during curing.

Due to time constraints and lack of equipment, the researchers were unable to test the fire resistance of the concrete specimens used for compression testing. Future studies should investigate whether the plastic melts and acts as a filler in cracks under high temperatures.

It is recommended to experiment with different levels of partial polystyrene replacement for gravel to determine whether partial replacement yields better compressive strength than full replacement.

This experiment was limited to determining compressive strength for concrete with fully replaced gravel. The researchers suggest conducting tensile strength tests as well.

Finally, it is recommended that future research be explored a variety of polymers and not limited solely to recycled polystyrene.

6. ACKNOWLEDGMENTS

The authors would like to thank the support of Pakvite Manufacturing Corporation as a resource for EPCA which is a vital component of this study. The authors would also like to thank De La Salle University for the support especially Mr. Bernardo Bernardo for aiding the team during the experimentation process and for the guide in the use of tools and equipment needed to complete this research.

7. REFERENCES

- [1] HHao, Y., and Shafer, G, Models for Predicting Global Plastic Waste, Aresty Rutgers Undergraduate Research Journal, Vol. 1, Issue 2, 2021, <https://doi.org/10.14713/arestyrurj.v1i2.154>.
- [2] Wibowo, A. P, The Strength and Water Absorption of Heated Expanded Polystyrene Beads Lightweight-concrete, International Journal of GEOMATE, Vol. 21, Issue 83, 2021, <https://doi.org/10.21660/2021.83.j2146>.
- [3] Long, H. V, Influence of Coarse Aggregates and Mortar Matrix on Properties of Lightweight

- Aggregate Concretes, *International Journal of GEOMATE*, Vol. 19, Issue 75, 2020, <https://doi.org/10.21660/2020.75.45596>.
- [4] Dafalla, M, Influence of Density and Thickness on Polystyrene Insulated Concrete Block Walls, *International Journal of GEOMATE*, Vol. 17, Issue 59, 2019, <https://doi.org/10.21660/2019.59.8108>
- [5] Al-Alusi, M. R. M., Kurdi, N. H., Al-Hadithi, A. I., and Hammad, A, An Experimental Investigation of the Mechanical Characteristics and Drying Shrinkage of a Single-size Expanded Polystyrene Lightweight Concrete Reinforced With Waste Plastic Fibres, *Construction & Building Materials*, Vol. 415, 135048, 2024, <https://doi.org/10.1016/j.conbuildmat.2024.135048>.
- [6] Lejano, B., Elevado, K.J., Fandiño, M.A., Ng, E.A., Datinguino, Z.A.N., and Oliveros, S.B., Experimental Investigation of Utilizing Coconut Shell Ash and Coconut Shell Granules as Aggregates in Coconut Coir Reinforced Concrete. *Cleaner Engineering and Technology*, Vol. 21, 100779, 2024, DOI: <https://doi.org/10.1016/j.clet.2024.100779>.
- [7] Scheirs, J., and Priddy, D. B., *Modern Styrenic Polymers: Polystyrenes and Styrenic Copolymers*, John Wiley & Sons, Ltd, 2003.
- [8] Nursyamsi, and Zebua, W. S. B., The Influence of Pet Plastic Waste Gradations as Coarse Aggregate Towards Compressive Strength of Light Concrete, *Procedia Engineering*, Vol. 171, pp. 614–619, 2018, <https://doi.org/10.1016/j.proeng.2017.01.394>.
- [9] Purnomo, H., Pamudji, G., and Satim, M., Influence of Uncoated and Coated Plastic Waste Coarse Aggregates to Concrete Compressive Strength, *MATEC Web of Conferences*, Vol. 101, 01016, 2017.
- [10] Saikia, N., and De Brito, J., Waste Polyethylene Terephthalate as an Aggregate in Concrete, *Materials Research*, Vol. 16, Issue 2, 2013, pp. 341–350.
- [11] Choi, Y., Moon, D., Chung, J., and Cho, S., Effects of Waste Pet Bottles Aggregate on the Properties of Concrete, Cement and Concrete Research, Vol. 35, Issue 4, 2005, pp. 776–781, <https://doi.org/10.1016/j.cemconres.2004.05.014>.
- [12] Hamad, A. J., Size and Shape Effect of Specimen on the Compressive Strength of Hplwfc Reinforced With Glass Fibres. *Journal of King Saud University-Engineering Sciences*, Vol. 29, Issue 4, 2017, pp. 373-380.
- [13] American Concrete Institute, *Topics in Concrete*. American Concrete Institute. Retrieved November 24, 2022, from <https://www.concrete.org/topicsInConcrete/topicdetail/aggregate?search=aggregate>.
- [14] Zhang, M.H and Gjvorv, O. E., Mechanical Properties of High-Strength Lightweight Concrete, *Materials Journal*, Vol. 88, Issue 3, 1991, pp. 240–247.
- [15] Shelorkar, A. P., and Jadhao, P. D., Effect of Varying Water Cement Ratio on Modulus of Elasticity of High-performance Fibre-reinforced Concrete (HPFRC). *Materials Today: Proceedings*, Vol. 65, 2022, pp. 784–791, <https://doi.org/10.1016/j.matpr.2022.03.289>
- [16] Neville, G. B., Chapter 3: The Strength of Concrete, In *Concrete Manual: 2012 IBC and ACI 318-11 Concrete Quality and Field Practices*, pp. 23–27, Essay, International Code Council, 2012.
- [17] Lejano, B., Elevado, K.J., Jarder, S.L., Arion, J.L., Capistrano, N.S., Ongpeng, Z., and Perez, A., Enhancing Compressive Strength in Concrete With Waste Ceramic Tiles: Effects of Selected Aggregate Modification Treatments, Water-cement Ratio and Curing Periods for Decision Tree Regression Analysis. *Journal of Engineering Science & Technology*, Vol. 19, Issue 3, 2024, pp. 744-761.

Copyright © Int. J. of GEOMATE All rights reserved, including making copies, unless permission is obtained from the copyright proprietors.
